

Curie temperature determination of $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$ permanent magnet alloys

L. P. Barbosa, H. Takiishi, R. N. Faria*
D. Rodrigues, S. Janasi**

Instituto de Pesquisas Energeticas e Nucleares, IPEN-CNEN
S. Paulo, Brazil
Instituto de Pesquisas Tecnológicas, IPT
S. Paulo, Brazil,
[luzinete@net.ipen.br*](mailto:luzinete@net.ipen.br)

Keywords: : Pr-based alloys; magnetic materials; hydrides; magnetic properties

Abstract: This paper reports the results of investigations carried out to determine the Curie temperature (T_c) of some annealed praseodymium-based alloys represented by the formula $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$. The Curie temperature of these permanent magnet alloys increase linearly with the cobalt content at about $(10.2 \pm 0.3)^\circ\text{C}/\text{at}\%$. $\text{Pr}_{14}\text{Fe}_{80}\text{B}_6$ and $\text{Pr}_{14}\text{Fe}_{79.9}\text{B}_6\text{Nb}_{0.1}$ magnetic alloys with a T_c of 290°C have been used as a standard reference. Magnets were prepared from the alloys using the hydrogenation, disproportionation, desorption and recombination (HDDR) process.

Introduction

In the past, Pr-Fe-B HDDR bonded magnets with high anisotropy have only been produced with substitutions of Co, Zr and Nb [1-5]. Recently, it has been shown the influence of the cobalt and niobium content on the magnetic properties of PrFeCoBNb-type HDDR magnets [6, 7]. The microstructures of these alloys also changed considerably with the addition element content [6]. The Curie temperature of the Nd-based alloy (310°C) is slight higher than that of the Pr-based alloy (290°C) [5]. Cobalt-containing alloys and magnets have a higher Curie temperature in comparison to the conventional Nd-Fe-B or Pr-Fe-B materials due to the substitution of Co for Fe in the matrix phase. It has been reported that the Curie temperature of the $\text{Nd}_2\text{Fe}_{14}\text{B}$ phase increases linearly with the Co content at about 11°C per at% [5, 8]. Similar increase in T_c has also been reported for $\text{Nd}_{13.7}\text{Fe}_{63.5}\text{Co}_{16.7}\text{B}_6\text{Zr}_{0.1}$ ($T_c=485^\circ\text{C}$) and $\text{Pr}_{13.7}\text{Fe}_{63.5}\text{Co}_{16.7}\text{B}_6\text{Zr}_{0.1}$ ($T_c=465^\circ\text{C}$) alloys [5]. This paper reports the results of further work carried out on $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$ -type alloys and HDDR magnets (where $x = 0, 4, 8, 10, 12, 16$). This investigation was undertaken to systematically determine the Curie temperature of these materials as a function of the cobalt content and also to verify if a similar linear increase of $11^\circ\text{C}/\text{at}\%$ applies to the Pr-Fe-Co-B-Nb based materials.

Materials and Methods

Various commercial alloys in the homogenized state were studied. Homogenisation heat treatment was carried out by annealing the as-cast alloys in vacuum at 1100°C for 20 h.

The details of the preparation of the HDDR bonded magnets, alloy annealing and magnetic measurements have all been described in previous papers [1-6]. A susceptibility analyser was employed for thermomagnetic analysis (TMA) of the alloys in order to investigate their susceptibility versus temperature behaviour over the temperature range 50-500°C. A magnetic field of low amplitude (333 Hz) and a heating rate of 1°C/min were employed in this study. Permeameter measurements were performed after saturation in a pulsed field of 6.0 T. Remanence values have been normalized assuming 100% density for the HDDR sample, and by also considering a linear relationship between density and remanence.

Results and Discussion

The variation in Curie temperature of the annealed Pr-based alloys as a function of cobalt content is shown in Fig. 1. The calculated or theoretical Curie temperature of the Pr-Fe-B-Nb alloys with Co additions, plotted as a solid line, was based on a $\text{Pr}_2\text{Fe}_{14}\text{B}$ phase with a Curie temperature of 290°C increasing 11°C per at% Co (assuming the same behaviour as the Nd-based materials). The Curie temperature of the $\text{Pr}_2\text{Fe}_{14}\text{B}$ matrix phase without addition of cobalt, determined previously by differential thermal analysis (DTA), was around 290°C [9]. This value was slightly higher than that determined in the same study using TMA (282°C). This phase also has various reported Curie temperatures such as 303°C [10], 290°C [11] and 284°C [12]. Thus in the present study the chosen reference temperature for the $\text{Pr}_2\text{Fe}_{14}\text{B}$ phase was 290°C. Good agreement was obtained between the measured and the calculated values. A linear fit for the TMA measured values showed that the Curie temperature of the $\text{Pr}_2\text{Fe}_{14}\text{B}$ phase increases linearly with the Co content at about 10.2°C per at%. Therefore, not only the Curie temperature of Pr-based is inferior to that of Nd-based materials but also the rate of increase with cobalt content. The thermomagnetic curves showing the Curie temperature for the $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$ -type alloys in the annealed condition are presented in Fig. 2. Very well defined susceptibility variation is observed in all the magnetic alloys on the Curie temperature.

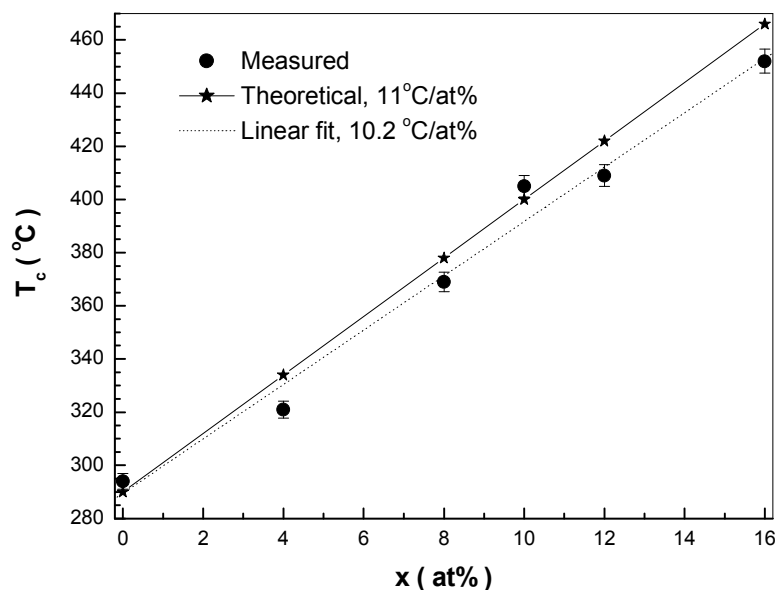


Fig.1 - Curie temperature versus cobalt content for $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$ -type HDDR magnets.

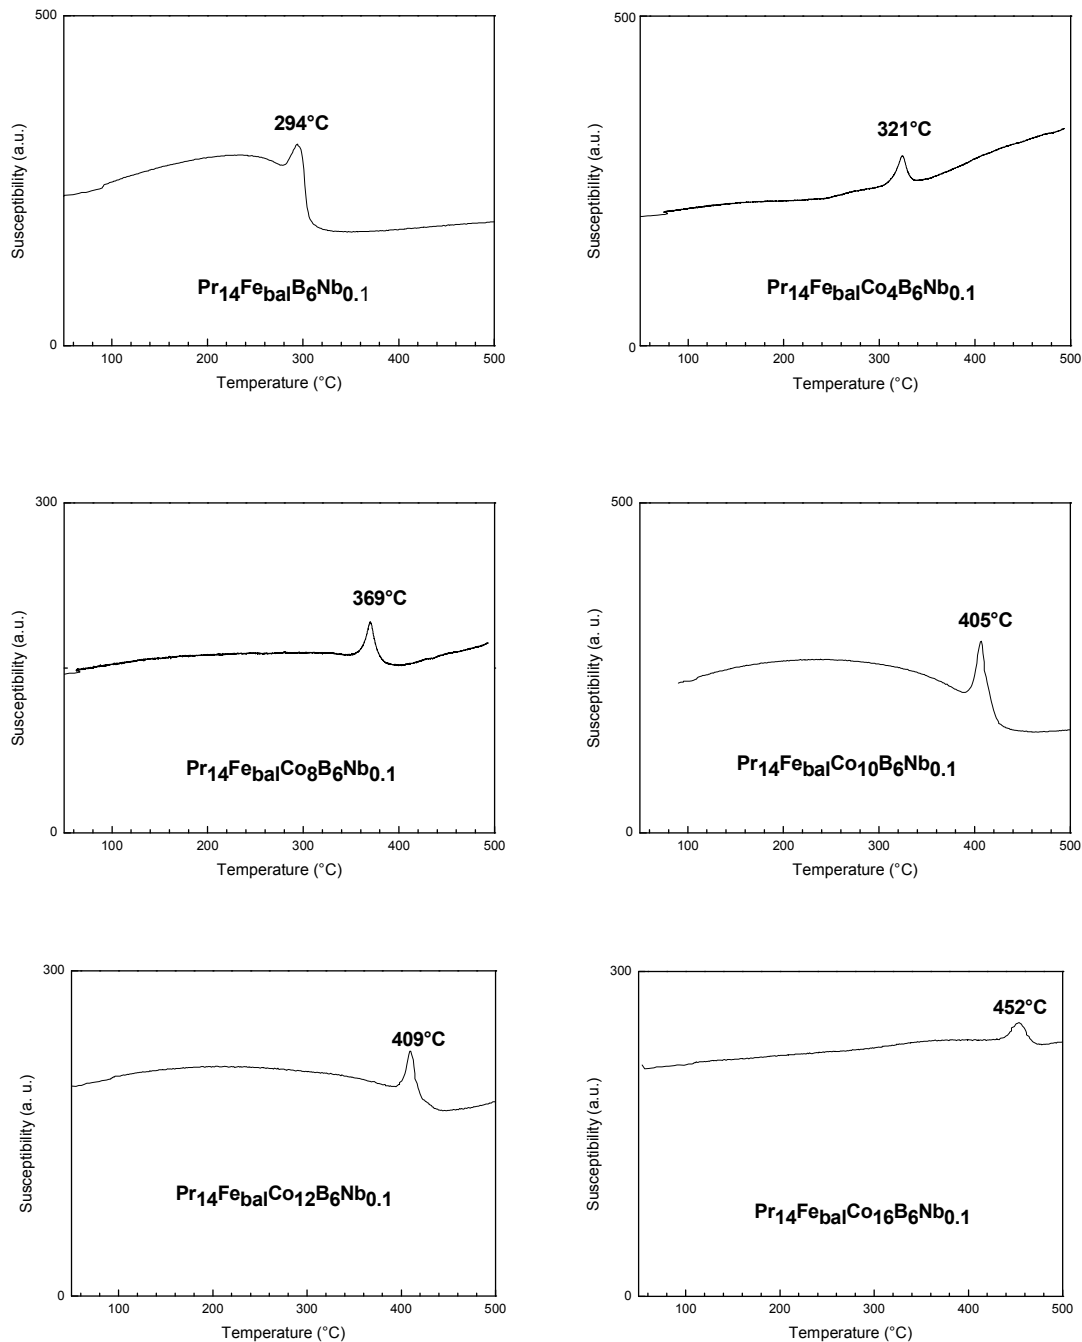


Fig.2 - Thermomagnetic curves for the $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$ -type alloys in the annealed condition ($x = 0, 4, 8, 10, 12, 16$).

The variation in remanence and intrinsic coercivity of HDDR magnets, produced from annealed Pr-based alloys, as a function of cobalt content is shown in Figure 3. Good remanence values were achieved in samples prepared from annealed Co-containing alloys. In the presence of 8.0 at.% Co, the remanence increased from 0.79 to 0.84 T, which was the highest remanence value. Higher Co contents produced a slight decrease in remanence. In the presence of 4.0 at.% cobalt, a magnet with the best intrinsic coercivity (0.97 MA/m) was

obtained. At higher Co contents this magnetic property decreased substantially. It was also noted that the HDDR magnet produced using the Co-free alloy in the annealed condition presented good intrinsic coercivity (0.92 MA/m).

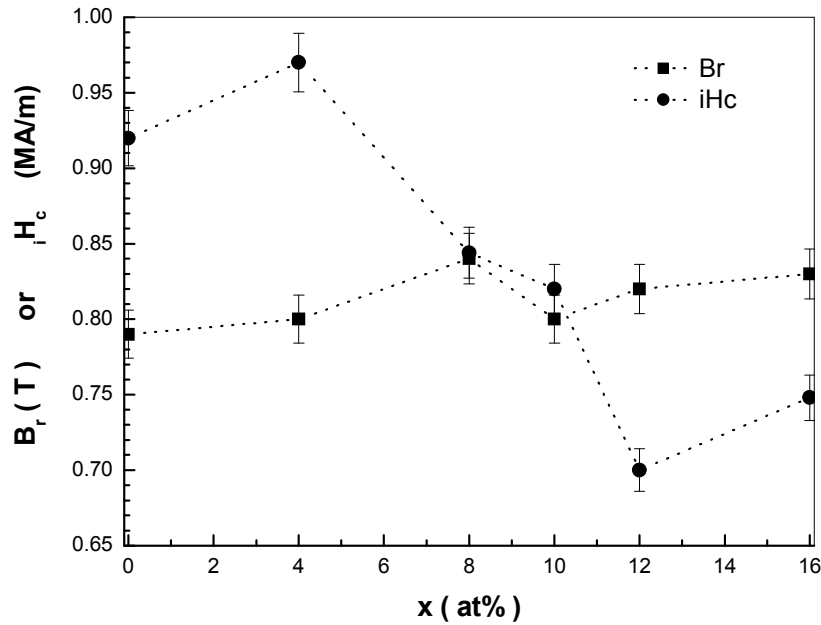


Fig.3 - Remanence and intrinsic coercivity versus cobalt content for $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$ -type HDDR magnets produced from annealed alloys.

A summary of the magnetic properties and Curie temperature of all the magnets produced with the praseodymium-based alloys in the annealed condition are shown in Table 1. The best energy product (121 kJ/m^3) was observed in the magnet containing 8 at.% cobalt. Niobium addition increased the remanence from 0.68 to 0.79 T in HDDR magnets prepared from annealed Co-free alloys but had no effect on coercivity. The highest intrinsic coercivity (0.97 MA^{-1}) was observed in the HDDR magnet containing only 4 at.% cobalt.

Table 1 - Magnetic properties and Curie temperature of Pr-type magnets.

| Composition | B_r (T) | iH_c (MA/m) | $(BH)_{\max}$ (kJm^{-3}) | T_c ($^{\circ}\text{C}$) |
|---|-----------------|------------------|--|---------------------------------|
| $\text{Pr}_{14}\text{Fe}_{80}\text{B}_6$ | 0.68 ± 0.01 | 0.92 ± 0.02 | 81 ± 2 | 299 ± 1.5 |
| $\text{Pr}_{14}\text{Fe}_{79.9}\text{B}_6\text{Nb}_{0.1}$ | 0.79 ± 0.02 | 0.92 ± 0.02 | 114 ± 2 | 294 ± 1.5 |
| $\text{Pr}_{14}\text{Fe}_{75.9}\text{Co}_4\text{B}_6\text{Nb}_{0.1}$ | 0.80 ± 0.02 | 0.97 ± 0.02 | 111 ± 2 | 321 ± 1.6 |
| $\text{Pr}_{14}\text{Fe}_{71.9}\text{Co}_8\text{B}_6\text{Nb}_{0.1}$ | 0.84 ± 0.02 | 0.84 ± 0.02 | 121 ± 2 | 369 ± 1.8 |
| $\text{Pr}_{14}\text{Fe}_{69.9}\text{Co}_{10}\text{B}_6\text{Nb}_{0.1}$ | 0.80 ± 0.02 | 0.82 ± 0.02 | 107 ± 2 | 405 ± 2.0 |
| $\text{Pr}_{14}\text{Fe}_{67.9}\text{Co}_{12}\text{B}_6\text{Nb}_{0.1}$ | 0.82 ± 0.02 | 0.70 ± 0.01 | 113 ± 2 | 409 ± 2.0 |
| $\text{Pr}_{14}\text{Fe}_{63.9}\text{Co}_{16}\text{B}_6\text{Nb}_{0.1}$ | 0.83 ± 0.02 | 0.75 ± 0.01 | 101 ± 2 | 452 ± 2.3 |
| $\text{Pr}_{14}\text{Fe}_{64.0}\text{Co}_{16}\text{B}_6$ | 0.70 ± 0.01 | 0.75 ± 0.01 | 80 ± 2 | 456 ± 2.3 |

Conclusions

The Curie temperature of the $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$ permanent magnet alloys increase linearly with the cobalt content at about $(10.2 \pm 0.3)^\circ\text{C}/\text{at}\%$, rate which is slightly inferior to that reported for neodymium-iron-boron-based materials (11°C per at%). Bonded magnets produced with these magnetic alloys exhibited a non-linear behaviour as far as remanence and intrinsic coercivity are concerned. Only $\text{Pr}_{14}\text{Fe}_{75.9}\text{Co}_4\text{B}_6\text{Nb}_{0.1}$ and $\text{Pr}_{14}\text{Fe}_{71.9}\text{Co}_8\text{B}_6\text{Nb}_{0.1}$ HDDR powders produced from annealed alloys yielded magnets with good overall magnetic properties. The former exhibited better intrinsic coercivity (0.97 MA m^{-1}) and the latter an improved remanence (0.84 T).

Acknowledgements

The authors wish to thank FAPESP and IPEN-CNEN/SP for the financial support and infrastructure made available to carry out this investigation.

References

- [1] Y. B. Kim, W. Y. Jeung, *J. Appl. Phys.* 83 (1) (1998), p. 6405
- [2] R.N. Faria, A.J. Williams, I.R. Harris, *J. Alloys and Comp.* 287 (1999), L10-L12.
- [3] R.N. Faria, A.J. Williams, I.R. Harris, *J. Magn. Magn. Mater* 202 (1999), p. 349
- [4] R.N. Faria, D.N. Brown, I.R. Harris, *J. Alloys and Comp.* 296 (2000), p. 219
- [5] R.N. Faria, B. E. Davies, D.N. Brown, I.R. Harris, *J. Alloys and Comp.* 296 (2000), p. 223
- [6] L. P. Barbosa, H. Takiishi, R.N. Faria, *J. Magn. Magn. Mater.* 268 (2004), p. 132.
- [7] L. P. Barbosa, H. Takiishi, L. F. C. P. Lima, R.N. Faria, *J. Magn. Magn. Mater.* 283 (2004), p. 263.
- [8] R. S. Mottram, PhD. Thesis, University of Birmingham, (1998), p. 109.
- [9] R.N. Faria, X. J. Yin, J. S. Abell, I.R. Harris, *J. Magn. Magn. Mater* 129 (1994), p. 263.
- [10] S. Y. Jiang, H. Y. Chen, S. F. Cheng, E. B. Boltich, S. G. Sankar, D. E. Laughlin, W. E. Wallace, *J. Appl. Phys.* 64 (1988), p. 5510.
- [11] J. Jinghua, H. Yiyang, L. Jingkui, *Scientia Sinica (Series A)* V-XXX (1987), p. 607.
- [12] N. Takahashi, H. Nakamura, C. R. Paik, S. Sugimoto, M. Okada, M. Homma, *Matter. Trans. Jpn. Inst. Metals* 32 (1991), p. 90.

Advanced Powder Technology V

doi:10.4028/www.scientific.net/MSF.530-531

Curie Temperature Determination of Pr₁₄Fe_{79.9-x}Co_xB₆Nb_{0.1} Permanent Magnet Alloys

doi:10.4028/www.scientific.net/MSF.530-531.176